



**INTERNATIONAL JOURNAL OF ENGINEERING SCIENCES & RESEARCH
TECHNOLOGY**

**AN EXPERIMENTAL STUDY ON EFFECT OF SILICA FUME & FLY ASH IN SLAG
CONCRETE**

D. Ravi Kumar*, V. Bhargavi

*Structural Engineering, Dept.of Civil Engg., Visakha Technical Campus, Visakhapatnam,
Andhra Pradesh, INDIA

M.E(Structural Engineering), ASSISTANT PROFESSOR, Visakha Technical Campus,
Visakhapatnam, Andhra Pradesh, INDIA

ABSTRACT

Concrete is the most versatile construction material because it can be designed to withstand the harshest environments while taking on the most inspirational forms. Engineers are continually pushing the limits to improve its performance with the help of innovative chemical admixtures and supplementary cementitious materials. Nowadays, most concrete mixture contains supplementary cementitious material which forms part of the cementitious component. These materials are majority byproducts from other processes. The main benefits of SCMs are their ability to replace certain amount of cement and still able to display cementitious property, thus reducing the cost of using Portland cement. The fast growth in industrialisation has resulted in tons and tons of byproduct or waste materials, which can be used as SCMs such as fly ash, silica fume, ground granulated blast furnace slag, steel slag etc. The use of these byproducts not only helps to utilize these waste materials but also enhances the properties of concrete in fresh and hydrated states. Slag cement and fly ash are the two most common SCMs used in concrete. Most concrete produced today includes one or both of these materials. For this reason their properties are frequently compared to each other by mix designers seeking to optimize concrete mixtures. Perhaps the most successful SCM is silica fume because it improves both strength and durability of concrete to such extent that modern design rules call for the addition of silica fume for design of high strength concrete. To design high strength concrete good quality aggregates is also required. Steel slag is an industrial byproduct obtained from the steel manufacturing industry. This can be used as aggregate in concrete. It is currently used as aggregate in hot mix asphalt surface applications, but there is a need for some additional work to determine the feasibility of utilizing this industrial byproduct more wisely as a replacement for both fine and coarse aggregates in a conventional concrete mixture. Replacing all or some portion of natural aggregates with steel slag would lead to considerable environmental benefits. Steel slag aggregate generally exhibit a propensity to expand because of the presence of free lime and magnesium oxides hence steel slag aggregates are not used in concrete making. Proper weathering treatment and use of pozzolanic materials like silica fume with steel slag is reported to reduce the expansion of the concrete. However, all these materials have certain shortfalls but a proper combination of them can compensate each other's drawbacks which may result in a good matrix product with enhance overall quality.

In the present work a series of tests were carried out to make comparative studies of various mechanical properties of concrete mixes prepared by using ACC brand Slag cement , Fly ash cement and their blend (in 1:1 proportion). These binder mixes are modified by 10% and 20% of silica fume in replacement. The fine aggregate used is natural sand comply to zone II as per IS 383-1982.The coarse aggregate used is steel making slag of 20 mm down size. The ingredients are mixed in 1: 1.5: 3 proportions. The properties studied are 7days, 28days and 56 days compressive strengths, flexural strength, porosity, capillary absorption.

The main conclusions drawn are inclusion of silica fume increases the water requirement of binder mixes to make paste of normal consistency. Water requirement increase with increasing dose of silica fume. Water requirement is more with fly ash cement than slag cement. The same trend is obtained for water binder ratio while making concrete to achieve a target slump of 50-70 mm. The mortar strength (1:3) increases with increasing percentage of silica fume. Comparatively higher early strength gain (7-days) is obtained with fly ash cement while later age strength (28 days) gain is obtained with slag cement. Their blended mix shows comparatively moderate strength gain at both early and later ages. Mixing of silica fume had made concrete sticky ie more plastic specifically with fly ash cement. The porosity and capillary absorption tests conducted on mortar mixes show decrease in capillary absorption and porosity

with increase in silica fume percentage with both types of cements. The decrease is more with fly ash cement than slag cement. But the reverse pattern is obtained for concrete i.e. the results show decrease in 7 days, 28 days and 56 days compressive strength of concrete due to inclusion of silica fume in the matrix. The increasing dose of silica fume show further decrease in strength at every stage. Almost same trend is obtained for flexural strength also. The specimens without silica fume had fine cracks which are more visible in concrete made with slag cement than fly ash cement.

KEYWORDS: Silica FUME, FLY ASH

INTRODUCTION

Concrete is a mixture of cement, sand, coarse aggregate and water. Its success lies in its versatility as can be designed to withstand harshest environments while taking on the most inspirational forms. Engineers and scientists are further trying to increase its limits with the help of innovative chemical admixtures and various supplementary cementitious materials SCMs.

Early SCMs consisted of natural, readily available materials like volcanic ash or diatomaceous earth. The engineering marvels like Roman aqueducts, the Coliseum are examples of this technique used by Greeks and Romans. Nowadays, most concrete mixture contains SCMs which are mainly byproducts or waste materials from other industrial processes.

SUPPLEMENTARY CEMENTITIOUS MATERIAL

More recently, strict environmental – pollution controls and regulations have produced an increase in the industrial wastes and sub graded byproducts which can be used as SCMs such as fly ash, silica fume, ground granulated blast furnace slag etc. The use of SCMs in concrete constructions not only prevent these materials to check the pollution but also to enhance the properties of concrete in fresh and hydrated states.

The SCMs can be divided in two categories based on their type of reaction : hydraulic and pozzolanic. Hydraulic materials react directly with water to form cementitious compound like GGBS. Pozzolanic materials do not have any cementitious property but when used with cement or lime react with calcium hydroxide to form products possessing cementitious prosperities.

Ground granulated blast furnace Slag: It is hydraulic type of SCM.

Ground granulated blast furnace slag (GGBS or GGBFS) is obtained by quenching molten iron slag ,a by-product of iron and steel making from a blast furnace in water or steam, to produce a glassy, granular product that is then dried and ground into a fine powder.

Ground granulated blast furnace slag (GGBFS) has been utilized for many years as an additional cementitious material in Portland cement concretes, either as a mineral admixture or as a component of blended cement. Granulated blast furnace slag typically replaces 35–65% Portland cement in concrete. The use of GGBFS as a partial replacement of ordinary Portland cement improves strength and durability of concrete by creating a denser matrix and thereby increasing the service life of concrete structures. It has a higher proportion of the strength-enhancing calcium silicate hydrates (CSH) than concrete made with Portland cement only, and a reduced content of free lime, which does not contribute to concrete strength.

Fly ash: It is pozzalanic SC material

Fly ash is one of the residues generated in the combustion of coal. Fly ash is generally captured from the chimneys of coal-fired power plants, and is one of two types of ash that jointly are known as **coal ash**; the other, bottom ash, is removed from the bottom of coal furnaces. Depending upon the source and makeup of the coal being burned, the components of fly ash vary considerably, but all fly ash includes substantial amounts of silicon dioxide (SiO₂) (both amorphous and crystalline) and calcium oxide (CaO). Fly ash is classified as Class F and Class C types

The replacement of Portland cement with fly ash is considered to reduce the greenhouse gas "footprint" of concrete, as the production of one ton of Portland cement produces approximately one ton of CO₂ as compared to zero CO₂ being produced using existing fly ash. New fly ash production, i.e., the burning of coal, produces approximately twenty to thirty tons of CO₂ per ton of fly ash. Since the worldwide production of Portland cement is expected to reach nearly 2 billion tons by 2010, replacement of any large portion of this cement by fly ash could significantly reduce carbon

emissions associated with construction.

It has been used successfully to replace Portland cement up to 30% by mass, without adversely affecting the strength and durability of concrete. Several laboratory and field investigations involving concrete containing fly ash had reported to exhibit excellent mechanical and durability properties. However, the pozzolanic reaction of fly ash being a slow process, its contribution towards the strength development occurs only at later ages. Due to the spherical shape of fly ash particles, it can also increase workability of cement while reducing water demand

Silica Fume: It is also a type of pozzolanic material.

Silica fume is a byproduct in the reduction of high-purity quartz with coke in electric arc furnaces in the production of silicon and ferrosilicon alloys. Silica fume consists of fine particles with a surface area on the order of 215,280 ft²/lb (20,000 m²/kg) when measured by nitrogen adsorption techniques, with particles approximately one hundredth the size of the average cement. Because of its extreme fineness and high silica content, silica fume is a very effective pozzolanic material particle.

Silica fume is added to Portland cement concrete to improve its properties, in particular its compressive strength, bond strength, and abrasion resistance. These improvements stem from both the mechanical improvements resulting from addition of a very fine powder to the cement paste mix as well as from the pozzolanic reactions between the silica fume and free calcium hydroxide in the paste. Addition of silica fume also reduces the permeability of concrete to chloride ions, which protects the reinforcing steel of concrete from corrosion, especially in chloride-rich environments such as coastal regions. When silica fume is incorporated, the rate of cement hydration increases at the early hours due to the release of OH⁻ ions and alkalis into the pore fluid. The increased rate of hydration may be attributable to the ability of silica fume to provide nucleating sites to precipitating hydration products like lime, C₃S+H, and ettringite. It has been reported that the pozzolanic reaction of silica fume is very significant and the non-evaporable water content decreases between 90 and 550 days at low water/binder ratios with the addition of silica fume.

During the last decade, considerable attention has been given to the use of silica fume as a partial replacement of cement to produce high-strength concrete.

STEEL SLAG

The Steel slag, a byproduct of steel making, is produced during the separation of molten steel from impurities in steel making furnaces. This can be used as aggregate in concrete. Steel slag aggregate generally exhibit a propensity to expand because of the presence of free lime and magnesium oxides that have not reacted with the silicate structure and that can hydrate and expand in humid environments. This potentially expansive nature (volume changes up to 10 percent or more attributable to the hydration of calcium and magnesium oxides) could cause difficulties with products containing steel slag, and is one reason why steel slag aggregate are not used in concrete construction. Steel slag is currently used as aggregate in hot mix asphalt surface applications, but there is a need for some additional work to determine the feasibility of utilizing this industrial by-product more wisely as a replacement for both fine and coarse aggregates in a conventional concrete mixture. Most of the volume of concrete is aggregates. Replacing all or some portion of natural aggregates with steel slag would lead to considerable environmental benefits. Steel slag has high specific gravity, high abrasion value than naturally available aggregate apart from the drawbacks like more water absorption, high alkalis. Therefore with proper treatments it can be used as coarse aggregate in concrete.

The production of a HSC may be hampered if the aggregates are weak. Weak and marginal aggregates are widespread in many parts of the world and there is a concern as to the production of HSC in those regions. Incorporation of silica fume is one of the methods of enhancing the strength of concrete, particularly when the aggregates are of low quality.

MATERIALS AND METHODOLOGY

MATERIALS

Silica Fume

Silica fume is a byproduct in the reduction of high-purity quartz with coke in electric arc furnaces in the production of silicon and ferrosilicon alloys. Silica fume consists of fine particles with a surface area on the order of 215,280 ft²/lb (20,000 m²/kg) when measured by nitrogen adsorption techniques, with particles approximately one hundredth the size of the average cement. Because of its extreme fineness and high silica content, silica fume is a very effective

pozzolanic material particle. Silica fume is added to Portland cement concrete to improve its properties, in particular its compressive strength, bond strength, and abrasion resistance. These improvements stems from both the mechanical improvements resulting from addition of a very fine powder to the cement paste mix as well as from the pozzolanic reactions between the silica fume and free calcium hydroxide in the paste. Addition of silica fume also reduces the permeability of concrete to chloride ions, which protects the reinforcing steel of concrete from corrosion, especially in chloride-rich environments such as coastal regions .When silica fume is incorporated, the rate of cement hydration increases at the early hours due to the release of OH $\dot{\gamma}$ ions and alkalis into the pore fluid. The increased rate of hydration may be attributable to the ability of silica fume to provide nucleating sites to precipitating hydration products like lime, C±S±H, and ettringite. It has been reported that the pozzolanic reaction of silica fume is very significant and the non-evaporable water content decreases between 90 and 550 days at low water /binder ratios with the addition of silica fume.

Physical Properties of silica fume.

Chemical Analysis of silica fume

The chemical analysis of silica fume is given below in TableNo 3.2. It is also compared wit

Silica fume	ASTM-C-1240	Actual Analysis
SiO ₂	85% min	86.7%
LOI	6% max	2.5%
Moisture	3%	0.7%
Pozz Activity Index	105% min	129%
Sp Surface Area	>15 m ² /gm	22 m ² /gm
Bulk Density	550 to 700	600
+45	10% max	0.7%

Steel Slag

Steel slag is the residue of steel production process and composed of silicates and oxides of unwanted elements in steel chemical composition. Fifty million tons per year of LD slag were produced as a residue from Basic Oxygen Process (BOP) in the world.

In order to use these slags in cement, its hydraulic properties should be known. Chemical composition is one of the important parameters determining the hydraulic properties of the slags. In general, it is assumed that the higher the alkalinity, the higher the hydraulic properties. If alkalinity is > 1.8, it should be considered as cementitious material.

Investigations were carried out also on the usability of steel slag as construction material under laboratory and practical conditions. For this application, the required properties are high compression strength, wear strength and resistance to climatic conditions. The most important criterion is volume stability, in which free CaO and MgO contents of the slag play an important role. Both oxides can go into reaction with water. Hydration causes volume expansion and affects stability of volume. This is one reason why steel slag aggregate are not suitable for use in Portland cement concrete b. But at the moment, most steel slag being used as unbound aggregate for asphalt concrete pavement in many countries.

Sieve Analysis of Steel slag

Sieve Analysis of steel slag is done to know the grade of the aggregate. This is given in Table 3.3

Sieve size	Wt Retain	Cum Wt Ret ⁿ	% Cu wt Ret ⁿ	% Passing
20 mm	270 gm	0.270 kg	5.4	94.6
12.5 mm	3522 gm	3.792 kg	75.84	21.16
10 mm	790 gm	4.582 kg	91.64	8.36
4.75 mm	334 gm	4.916 kg	98.62	1.68
Total	5000 gm			

No gradation was found from the above test.

Physical properties of Steel slag.

The different physical properties of steel slag are given below in Table No 3.4.

Material	Specific gravity	Water absorption in %
Steel slag	3.35	1.1%

XRD Analysis of Steel slag.

From XRD Analysis of steel slag we can find what type Alkalis present. These are tabulated in Table No 3.5.

Chemical Compound	Visible	Ref-Code	Score
Na ₂ O	Yes	03-1074	10
K ₂ O	Yes	77-2176	10

From above table we can conclude that some amount of Alkalis present in steel slag.

Fly ash cement

Fly ash, which is largely made up of silicon dioxide and calcium oxide, can be used as a substitute for Portland cement, or as a supplement to it. The materials which make up fly ash are pozzolanic, meaning that they can be used to bind cement materials together. Pozzolanic materials, including fly ash cement, add durability and strength to concrete.

Fly ash cement is also known as green concrete. It binds the toxic chemicals that are present in the fly ash in a way that should prevent them from contaminating natural resources. Using fly ash cement in place of or in addition to Portland cement uses less energy, requires less invasive mining, and reduces both resource consumption and CO₂ emissions.

Table No. 3.6

cement	Consistency in %	Specific gravity	Initial setting time	Final setting time
Fly ash cement	37.5	3	3 hour 50 min	11 hour 35 min
FC10	47			
FC20	55.5			

Xrd Analysis of Fly ash cement.

By XRD (X ray diffraction) Analysis we can know what type of chemical composition present in cement. This analysis were done in metallurgical dept. of NIT Rourkela. The chemical compound found in this analysis was listed below:

Table No 3.7

Chemical Compound	Visible	Reference Code	Score
Ca ₅ MgAl ₂ Si ₁₆ O ₉₀	Yes	13-0272	59
CaAl ₂ O ₄	Yes	34-0440	17
CaCO ₃	Yes	72-1937	20
(MgO) 0.593(FeO).41	Yes	77-2367	14
Mg(CO ₃)	Yes	80-0042	16

SLAG CEMENT

Slag cement has been used in concrete projects in the United States for over a century. Earlier usage of slag cement in Europe and elsewhere demonstrates that long-term concrete performance is enhanced in many ways. Based on these early experiences, modern designers have found that these improved durability characteristics help further reduce life-cycle costs, lower maintenance costs and makes concrete more sustainable. For more information on how slag cement is manufactured and it enhances the durability and sustainability of concrete

Physical Properties of Slag cement.

Before proceeding to experimental work , the physical properties of slag cement is determined. Consistency is the main properties of cement for determining water content for mortar. Vicat,,s apparatus is used to determine consistency, initial setting time and final setting time. Specific gravity of cement was determined by Lechatelier"s apparatus. The properties of slag cement is given in Table No. 3.9

Chemical Analysis of Slag cement

The chemical analysis of cement is done to know the amount of chemical composition present in cement. Its procedure is accordingly Vogel"s Inorganic Quantitative Analysis. This experiment was done in our institute chemistry laboratory. Here our aim is to determine actual chemical composition of the specimen provided by the company. The chemical analysis of slag cement is listed in Table No. 3.11.ble No 3.11

Chemical Compound	Slag Cement in (%)
SiO ₂	12
CaO	43
MgO	0.37
Fe ₂ O ₃	12
Al ₂ O ₃	26

SAND

Sand is a naturally occurring granular material composed of finely divided rock and mineral particles. The most common constituent of sand, in inland continental settings and non-tropical coastal settings, is silica (silicon dioxide, or SiO₂), usually in the form of quartz which, because of its chemical inertness and considerable hardness, is the most common mineral resistant to weathering. It is used as fine aggregate in concrete.

Sieve Analysis of sand

The Sieve Analysis of sand is carried out to know the zone of the sand. The results of sieve analysis is given in Table No. 3.12.

Sieve size	Weight Retained in gm	% passing
4.75 mm	16 gm	98.4
2.36 mm	11 gm	97.3
1.18 mm	65 gm	90.8
600 micron	391 gm	51.6
300 micron	420 gm	9.4
150 micron	82 gm	1.2
Total	1000 gm	-

From the sieve analysis result, Sand falls under Zone II.

Physical properties of sand.

Before going to do experimental work the physical properties of sand is determined like specific gravity and water absorption. The physical properties of sand is given below in Table No 3.13.

Fine aggregate	Specific gravity	Water absorption in %
Sand	2.65	0.6

LABORATORY TEST CONDUCTED:***Compressive Strength Test***

For each set six standard cubes were cast to determine 7-days, 28 days and 56 days compressive strength after curing. Also nine no. of cube was casted to know the compressive strength of concrete. The size of the cube is as per the IS 10086 – 1982.

Capillary absorption Test

Two cube specimens were cast for both (Mortar and concrete cube) to determine capillary absorption coefficients after 7 days, 28 days and 56 days curing. This test is conducted to check the capillary absorption of different binder mix mortar matrices which indirectly measure the durability of the different mortar matrices [8].

Wet-dry Test:

Concrete cube were dipped inside a sea water for 4 hours and then exposed to dry for 20 hours. Sea water is prepared by dissolved 35 g of salt (NaCl) in one liter water. Here cubes were dipped inside the Sea water for 56 days and its compressive strength were determined by compressive testing machine.

Compressive test by pulse velocity.

The strength of concrete is generally governed by the strength of cement paste. If the strength of paste can be measured, then we can find reasonable indication for strength of concrete. This strength can be measured on site by rebound hammer method. The rebound hammer is an instrument which provides quick and simple non-destructive test for obtaining an immediate indication for concrete strength in every part of structure.

Flexural Test

It is the ability of a beam or slab to resist failure in bending. The flexural strength of concrete is 12 to 20 percent of compressive strength. Flexural strength is useful for field control and acceptance for pavement. But now a days flexural strength is not used to determine field control, only compressive strength is easy to judge the quality of concrete. To determine the flexural strength of concrete four numbers of prism were casting. Then it was cured properly.
Flexural strength = PL/BD^2

Where P is load

L= Length of Prism.

B = Breadth of Prism.

D = Breadth of Prism

RESULTS AND DISCUSSIONS**EXPERIMENTAL STUDY ON CONCRETE CUBE.**

Here we prepared concrete with ratio 1:1.5:3 from different types of cement + silica fume replacement as binder mix, sand as fine aggregate and steel slag as coarse aggregate. Then its physical properties like capillary absorption, water/cement ratio, compressive strength, porosity, flexural strength, and wet-dry test was predicted. These test results both in tabular form and graphical presentation are given below.

Water /Cement Ratio and Slump.

The water cement ratio and slump of steel slag concrete with different binder mix with silica fume replacement is given below.

Type of cement	% of SF Replaced	W/C Ratio	Slump in (mm)
Fly ash cement	0	0.51	52
	10	0.58	52
	20	0.591	58
Slag cement	0	0.47	63
	10	0.518	50
	20	0.581	55
Slag and fly ash cement blend (1:1)	0	0.489	60
	10	0.543	53
	20	0.544	52

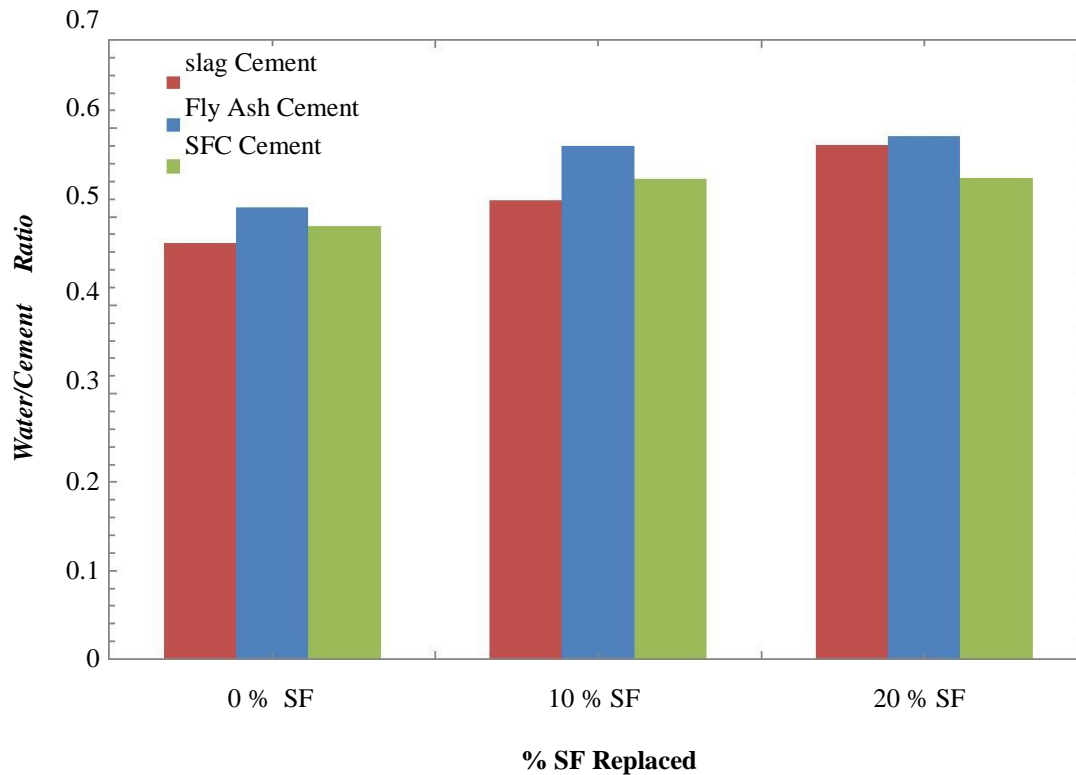


Figure.4.8 Water Cement Ratio for steel slag concrete

Compressive Strength by Rebound Hammer Method.

Compressive Strength of different concrete cubes after 7 days, 28 days and 56 days were tabulated in Table No. 4.7.

Type of cement	% of SF replaced	7 days	28 days	56 days
Fly ash cement	0	24.54	29.55	36.4
	10	21	25,7	25.94
	20	21.4	22.9	29.2
Slag cement	0	18.2	22.3	26.35
	10	18.6	22.3	27.4
	20	18.3	21.4	27.5
Slag and fly ash cement blend (1:1)	0	20.9	25.4	31.45
	10	21.8	23	27.44
	20	21.4	20.9	28.23

Compressive Strength by Compression Testing Machine.

Compressive Strength of different mortars after 7days ,28days and 56 days were tabulated in Table No. 4.8.

Table No 4.8

Type of cement	% of SF replaced	7days	28days	56 days
Fly ash cement	0	23.33	37.1	45.1
	10	21.61	27.77	30.44
	20	20.66	23.1	28
Slag cement	0	16.6	26.21	28.44
	10	18.44	25.33	25.55
	20	19.2	24.89	21.1
Slag and fly ash cement blend (1:1)	0	27.05	27.55	33.11
	10	22	23.77	29.77
	20	20	22.88	28.88

From the above table, we can conclude that early or 7 days strength, 28 days and 56 days strength decreases with increase in percentage of replacement by silica fume. This is due to the weak bond formation between cement paste and steel slag. There are lots of voids present in concrete, which is shown by SEM (Scanning Electron Microscope) Analysis, which are given below

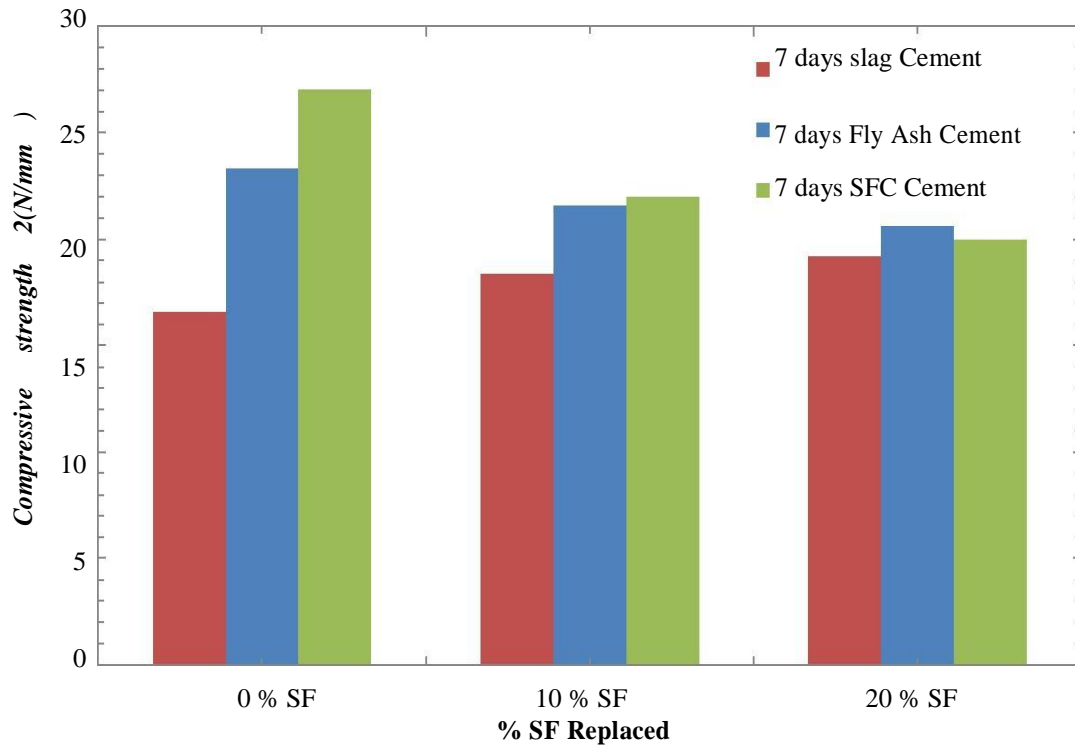


Figure.4.9 Compressive strength of concrete for 7 days

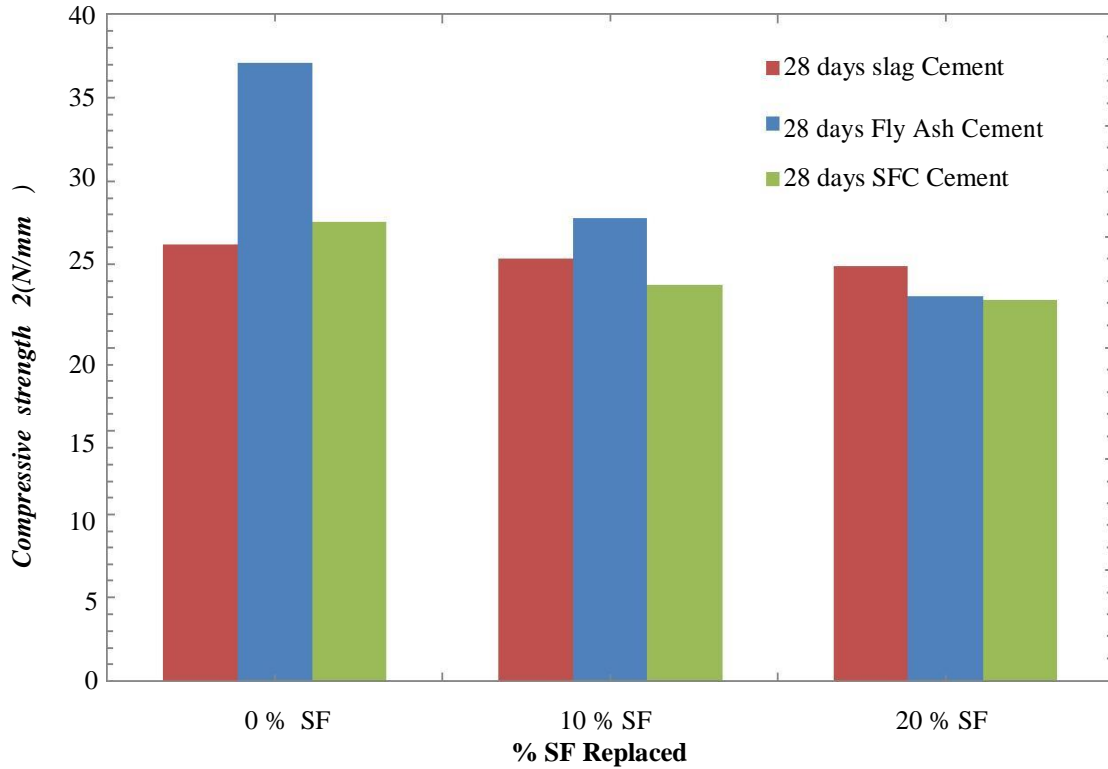


Figure.4.10 Compressive strength of concrete for 28 days

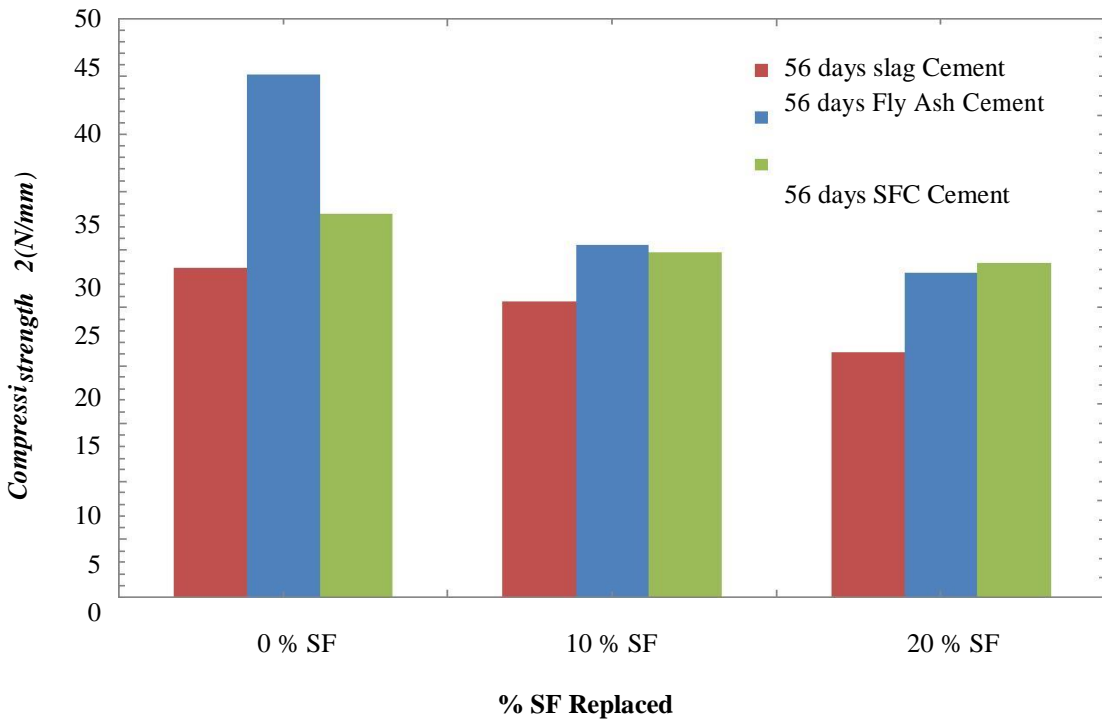


Figure.4.11 Compressive strength of concrete for 56 days

From the above graph, we can conclude that early or 7 days strength, 28 days and 56 days strength decreases with increase in percentage of replacement by silica fume. This is due to the weak bond formation between cement paste and steel slag. There are lots of voids present in concrete, which is shown by SEM (Scanning Electron Microscope) Analysis, which are given below

From the present study the following conclusions are drawn:

1. Inclusion of silica fume improves the strength of different types of binder mix by making them more denser.
2. Addition of silica fume improves the early strength gain of fly ash cement whereas it increases the later age strength of slag cement.
3. The equal blend of slag and fly ash cements improves overall strength development at any stage.
4. Addition of silica fume to any binder mix reduces capillary absorption and porosity because fine particles of silica fume reacts with lime present in cement and form hydrates dander and crystalline in composition.
5. The capillary absorption and porosity decreases with increase dose up to 20% replacement of silica fume for mortar.
6. Addition of silica fume to the concrete containing steel slag as coarse aggregate reduces the strength of concrete at any age.
7. This is due to the formation of voids during mixing and compacting the concrete mix in vibration table because silica fume make the mixture sticky or more cohesive which do not allow the entrapped air to escape. The use of needle vibrator may help to minimize this problem.
8. The most important reason of reduction in strength is due to alkali aggregate reaction between binder matrix and the steel slag used as coarse aggregate. By nature cement paste is alkaline. The presence of alkalis Na_2O , K_2O in the steel slag make the concrete more alkaline. When silica fume is added to the concrete, silica present in the silica fume react with the alkalis and lime and form a gel which harm the bond between aggregate and the binder matrix. This decrease is more prominent with higher dose of silica fume.
9. Combination of fly ash cement and silica fume makes the concrete more cohesive or sticky than the concrete containing slag cement and silica fume causing formation of more voids with fly ash cement. Therefore the concrete mixes containing fly ash and silica fume show higher capillary absorption and porosity than concrete mixes containing slag cement and silica fume.
10. The total replacement of natural coarse aggregate by steel slag is not recommended in concrete. A partial replacement with fly ash cement may help to produce high strength concrete with properly treated steel slag
11. The steel slag should be properly treated by stock piling it in open for at least one year to allow the free CaO & MgO to hydrate and thereby to reduce the expansion in later age.
12. A thorough chemical analysis of the steel slag is recommended to find out the presence of alkalis which may adversely affect to the bond between binder matrix and the aggregate.

REFERENCES

1. Thanongsak, N., Watcharapong, W., and Chaipanich. A., (2009), "Utilization of fly ash with silica fume and properties of Portland cement-fly ash-silica fume concrete". *Fuel*, Volume 89, Issue 3, March 2010, Pages 768-774.
2. Patel, A, Singh, S.P, Murmoo, M. (2009), "Evaluation of strength characteristics of steel slag hydrated matrix" Proceedings of Civil Engineering Conference-Innovation without limits (CEC-09), 1^{8th} - 1^{9th} September" 2009.
3. Li Yun-feng, Yao Yan, Wang Ling, "Recycling of industrial waste and performance of steel slag green concrete", *J. Cent. South Univ. Technol.*(2009) 16: 8-0773, DOI: 10.1007/s11771-009-0128-x.
4. Velosa, A.L, and Cachim, P.B., "Hydraulic lime based concrete: Strength development using a pozzolanic addition and different curing conditions" ,*Construction and Building Materials* ,Vol.23,Issue5,May2009,pp.2107-2111.
5. Barbhuiya S.A., Gbagbo, J.K., Russeli, M.I., Basheer, P.A.M. "Properties of fly ash concrete modified with hydrated lime and silica fume", "Centre for Built Environment Research, School of Planning, Architecture and Civil Engineering, Queen"s University Belfast, Northern Ireland BT7 1NN, United Kingdom Received

- 28 January 2009; revised 1 June 2009; accepted 3 June 2009. Available online 15 July 2009.
6. Gonen, T. and Yazicioglu, S. "The influence of mineral admixtures on the short and long term performances of concrete" department of construction education, Firat University, Elazig 23119, Turkey. 2009.
 7. Mateusz R.J. O. and Tommy N. "Effect of composition and Initial Curing Conditions of Scaling Resistance of Ternary(OPC/FA/SF) concrete", *Journal of Materials in Civil Engineering* © ASCE/October 2008, PP 668-677.
 8. -long, W QI, Yan-ming, He Jin-yun, "Experimental Study on Steel Slag and Slag Replacing Sand in Concrete", 2008, International Workshop on Modelling, Simulation and Optimization.
 9. Jigar P. Patel, "Broader use of steel slag aggregates in concrete", M.Tech.thesis, Cleveland State University, December, 2008.
 10. N.P. Rajamane *, J. Annie Peter, P.S. Ambily, "Prediction of compressive strength of concrete with fly ash as sand replacement material". *Cement and Concrete Composites*, Volume 29, Issue 3, March 2007, Pages 218-223.
 11. Abdullah A. Almusallam, Hamoud Beshr, Mohammed Maslehuddin, Omar S.B. Al-Amoudi, "Effect of silica fume on the mechanical properties of low quality coarse aggregate concrete", *Cement & Concrete Composites* 26 (2004) 891-900.
 12. Turkmen, I. "Influence of different curing conditions on the physical and mechanical properties of concrete with admixtures of silica fume and blast furnace slag", *Materials Letters* 57 (2003), pp.4560-4569. Article/View Record in Scopus/Cited by in Scopus(9).
 13. Tasdemir, C. "Combined effects of mineral admixtures and curing conditions on the sorptivity coefficient of concrete", *cement and concrete research* 33(2003), pp. 1637-1642.
 14. Thomas, M. D. A. and Shehata, M. H. "Use of ternary cementitious systems containing silica fume and fly ash in concrete"; *cement and concrete research* 29 (1999).
 15. Bijen, J. "Benefits of slag and fly ash" *construction and building materials*, vol. 10, no.5, pp. 309-314, 1996.
 16. Papadakis, V.G., M. Fardis, M.N., and Veyenas, C.G. "Hydration and carbonation of pozzolonic cements", *ACI materials journal technical paper* (1992) (89), pp. 305-316.
 17. Lam, L, Wong, Y.L., and Poon, C.S. "Effect of fly ash and silica fume on compressive and fracture behaviors of concrete" *Cement and Concrete research*, vol. 28, no. 2, pp. 271-283, 1988